Spin Liquid State in the 3D Frustrated Antiferromagnet $PbCuTe_2O_6$: NMR and μSR Studies

P. Khuntia*,[1,2] F. Bert,[2] P. Mendels,[2] B. Koteswararao,[3,4] A. V. Mahajan,[5]
M. Baenitz,[6] F. C. Chou,[4] C. Baines,[7] A. Amato,[7] and Y. Furukawa[1,8]

[1]*Ames Laboratory, US Department of Energy, Ames, Iowa 50011, USA*
[2]*Laboratoire de Physique des Solides, CNRS, Univ. Paris-Sud, Université Paris-Saclay, 91405 Orsay Cedex, France*
[3]*School of Physics, University of Hyderabad, Central University PO, Hyderabad 500046, India*
[4]*Center of Condensed Matter Sciences, National Taiwan University, Taipei 10617, Taiwan*
[5]*Department of Physics, Indian Institute of Technology Bombay Powai Mumbai-400076, India*
[6]*Max Planck Institute for Chemical Physics of Solids, 01187 Dresden, Germany*
[7]*Laboratory for Muon Spin Spectroscopy, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland*
[8]*Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA*

(Date text: updated version on:; Received textdate; Revised textdate; Accepted textdate; Published textdate)

arXiv:1602.05818v1 [cond-mat.str-el] 18 Feb 2016

Abstract

$PbCuTe_2O_6$ is a rare example of a spin liquid candidate featuring a three dimensional magnetic lattice. Strong geometric frustration arises from the dominant antiferromagnetic interaction which generates a hyperkagome network of Cu^{2+} ions although additional interactions enhance the magnetic lattice connectivity. Through a combination of magnetization measurements and local probe investigation by NMR and μSR down to 20 mK, we provide a robust evidence for the absence of magnetic freezing in the ground state. The local spin susceptibility probed by the NMR shift hardly deviates from the macroscopic one down to 1 K pointing to a homogeneous magnetic system with a low defect concentration. The saturation of the NMR shift and the sublinear power law temperature (T) evolution of the $1/T_1$ NMR relaxation rate at low T point to a non-singlet ground state favoring a gapless fermionic description of the magnetic excitations. Below 1 K a pronounced slowing down of the spin dynamics is witnessed, which may signal a reconstruction of spinon Fermi surface. Nonetheless, the compound remains in a fluctuating spin liquid state down to the lowest temperature of the present investigation.

PACS numbers: 75.40.Cx,75.10.Kt,76.60.-k, 76.60.Es, 74.40.Kb

Combining competing interactions and quantum fluctuations, maximized for low spin S = 1/2, is one major track followed in the past decade to discover novel disordered quantum states beyond the Landau paradigm of phase transition with broken symmetries. One such long sought state is a quantum spin liquid (QSL), breaking no symmetries down to $T = 0$ but exhibiting macroscopic entanglement of strongly interacting spins and featuring exotic fractionalized excitations [1, 2]. Much effort has been devoted towards low dimensional quantum antiferromagnets (AFM) where low lattice coordination helps in further destabilizing classical ground states in favor of more exotic ones driven by quantum fluctuations [3]. A few spin liquid materials have been identified, either based on the highly frustrated kagome lattice - a weakly coordinated ($z = 4$) network made of corner-sharing triangles - including the celebrated Herbertsmithite mineral [4–6], or based on the less frustrated simple triangular lattices ($z = 6$) [7, 8]. In three dimensional (3D) systems quantum states are even more elusive. In the double perovskite Ba_2YMoO_6 compound featuring edge-shared tetrahedra ($z = 12$), the Mo^{5+} ions host nearly pure spin $S = 1/2$ which quench partially into a valence bond glass state [9, 10]. Further developments in this context arise from some rare-earth based pyrochlores where large spins with strong anisotropies decorate corner-sharing tetrahedra ($z = 6$). The low energy physics can be mapped to a model of interacting effective spin S = 1/2 and may stabilize QSL states [11]. The hyperkagome structure - a 3D network of corner-sharing triangles ($z = 4$) offers an interesting alternative and indeed several exotic quantum phases relying on this geometry have been proposed [12]. At the origin of these studies is the $Na_4Ir_3O_8$ compound [13] where Ir^{4+} ions bear effective $J_{\rm eff} = 1/2$ spins and fail to order well below the exchange interaction energy although the ground state has recently been shown to be static [14, 15]. Whether perturbation terms to the Heisenberg model, such as exchange anisotropies, or disorder in the interaction is responsible for the low T freezing is still an open issue. Remarkably, those spin liquid candidates in 3D are based on rather heavy ions where the applicability of a model of S = 1/2 Heisenberg spins is questionable.

Recently, some of us reported a quantum AFM $PbCuTe_2O_6$ (henceforth PCTO), which constitutes a strongly frustrated 3D network of Cu^{2+} (S = 1/2) spins. $PbCuTe_2O_6$ crystallizes in a cubic structure with a hyperkagome magnetic lattice if only the dominant second nearest neighbor ($n.n.$) interaction J is considered [16]. Additionally, weaker 1st $n.n.$ ($\sim 0.5J$) and 3rd $n.n.$ ($\sim 0.8J$) AFM interactions form isolated triangles and chains. The magnetic susceptibility χ exhibits a Curie-Weiss (CW) behavior with an AFM $\theta_{CW} \simeq -22K$ and no sign of magnetic transition down to 2 K. The magnetic specific heat (C_m) shows a broad maximum at $T^{max} \simeq 0.05\theta_{CW} \simeq$ 1.1 K, quite similarly as in $Na_4Ir_3O_8$, followed by a weak kink at 0.87 K of unclear origin. In magnetic fields larger than 8 T, the evolution of C_m with temperature is nearly

quadratic at low *T*, in line with some theoretical predictions for the quantum hyperkagome model [17, 18].

In this Letter, we present a comprehensive account of the local magnetic susceptibility and low temperature spin dynamics via NMR and μSR measurements accompanied by low temperature magnetization studies on the highly frustrated 3D quantum antiferromagnet $PbCuTe_2O_6$. μSR data reveal no signature of long range magnetic ordering (LRO) down to 20 mK, a hallmark of a QSL state. The persistence of slow spin dynamics is confirmed by the NMR signal intensity being wiped out below 1 K and not recovered down to our lowest temperature *T* = 50 mK. Before the signal is lost, the NMR shift saturates at a finite value pointing to a non-singlet ground state.

Polycrystalline PCTO sample was synthesized by the method described in Ref. [16]. Fig. 1 shows the *T*-dependence of magnetic susceptibility. The magnetic susceptibility ($\chi = M/H$) displays a CW behavior at high-T and an enhancement at low temperature without any clear signature of LRO. A weak ZFC-FC splitting is nonetheless observed at 0.87 K at the lowest applied field of 0.01 T. At higher magnetic fields the irreversibility is suppressed but a kink remains detectable which slightly shifts towards lower *T*. This magnetic anomaly has to be connected to the kink in C_m at the same temperature (see inset of Fig.1). The relevance of this spin-glass like transition for the bulk properties of PCTO is difficult to decide on the sole basis of the macroscopic measurements. In the following we use local probe measurements and clearly demonstrate that the 0.87 K anomaly is not a bulk transition but is attributed to the presence of a tiny amount of defects in the polycrystaline sample.

To gain further insights into the spin dynamics and ground state properties, we have performed μSR measurements at Paul Scherrer Institute. The zero field relaxation of the polarization of the muons stopped in the sample could be fitted to a single stretched exponential model $P_z(t) = \exp[-(\lambda t)^{\beta}]$ in the whole temperature range (see Supplementary Material [20]). The monotonic decay of the polarization even at the lowest T= 20 mK demonstrates the absence of static internal field. In particular, the characteristic signatures of a frozen ground state, namely (damped) spontaneous oscillations and for a powder sample a non-zero polarization at long time due to internal fields directed along the initial muon polarization, are not observed in PCTO. The transition to static magnetism seen at 0.87 K in bulk magnetization measurements should therefore be attributed to a minority spin fraction undetected in the μSR experiment, $i.e.$ below a few percent of the sample volume. As detailed below, the fact that bulk spins slow down on the verge of static magnetism in this same temperature range, suggests nevetheless that the minority spin fraction does not constitute a separated impurity phase but could arise from some slightly disordered areas/grains in the polycrystalline sample.

The evolution of the relaxation rate (λ) and the stretched exponent β are shown in figure 2(b). The relaxation is close to exponential and hardly dependent on temperature above about 5 K indicating that the system is close to its paramagnetic limit [21]. At lower temperature, the increase of the relaxation rate renders evidence for a slowing down of the spin dynamics likely resulting from the building up of short range correlations. Upon further cooling below about 1 K, the increase steeply accelerates as if on the verge of a magnetic transition but then levels off below about 0.6 K. Such a saturation of λ is a common feature of highly frustrated magnets signaling the persistence of slow spin dynamics at $T \to 0$ in line with a QSL ground state.

The evolution of the relaxation shape from exponential ($\beta \sim 1$) to Gaussian ($\beta \sim 2$) across $\sim$ 1 K suggests that the electron spin fluctuations have slowed down substantially in the ground state at the limit of static magnetism. To quantify the level of fluctuations in the ground state, we have fitted the relaxation (see Fig. 2(a)) to the dynamical Kubo-Toyabe model [22] $P_{DKT}(t, \Delta H, \nu, H_{LF})$ which accounts for a gaussian distribution of internal fields of width ΔH fluctuating at the rate ν, in zero field or with an applied longitudinal field H_{LF}. In zero field, this model accounts well for the relaxation and gives $\Delta H = 1.1$ mT and $\nu = 0.7$ MHz. With a ratio $r = \gamma_\mu \Delta H/\nu \sim 1.3$ (where $\gamma_\mu = 2\pi \times 135.5$ Mrad/s is the muon gyromagnetic ratio), the Cu^{2+} spin fluctuations seem indeed to have slowed down to the quasi-static limit ($r \sim 1$) at base temperature. However, keeping these zero-field parameters, the model fails to account for the field dependence. Indeed in case of (quasi-)static magnetism one expects a strong reduction of the relaxation under an applied field of $\sim 5\Delta H \approx 5$ mT. Experimentally a field at least 20 times larger is needed to reach a similar reduction, implying a more dynamical scenario (Fig. 2(a)). Also surprising is the magnitude of the internal field, $\sim$ 1 mT which corresponds to a tiny moment $\sim 0.065\mu_B$ per Cu^{2+} ions obtained by estimating the dipolar field at the muon assumed to stop close to an oxygen site. These two features are strongly reminiscent of the "sporadic" model introduced to explain the "undecouplable gaussian shape" observed in the kagome bilayers chromates [23, 24]. This model assumes that the relaxation in the spin liquid state arises mostly from deconfined spinon excitations which pass close to the muon for only a fraction of time ft while the background ground state is hardly magnetic, if not a singlet state, giving no sizeable relaxation for the remaining time fraction $(1-f)t$. This results in a renormalization of the parameters of the dynamical Kubo Toyabe $P_z(t) = P_{DKT}(t, f\Delta H, fH_{LF}, f\nu)$. From the field dependence of $P_z(t)$, we estimate $f \sim 1/10$. A detailed comparison calls for specific measurements versus field and temperature which is beyond the scope of the present study, but gives a direction for further μSR studies.

In complex systems such as frustrated magnets where static magnetism and persistent fluctuations are often found to coexist at low temperatures, the comparison of different techniques with different time windows is necessary to get

a comprehensive understanding of the ground state properties. In addition to μSR experiments, ^{207}Pb (I = 1/2; $\gamma_n/2\pi$=8.874 MHz/T) NMR measurements were carried out. Shown in Fig. 3(a) are the field swept ^{207}Pb NMR spectra of PCTO at 63.5 MHz at different temperatures. The absence of major structural distortions/defects and a single ^{207}Pb nuclear site in the host lattice result in narrow spectra. This offers the opportunity to track the local magnetic susceptibility unambiguously. Shown in Fig. 3(b) is the integrated NMR signal intensity, after taking into account the spin-spin relaxation T_2 correction [20]. Remarkably, the intensity decreases drastically below 1.6 K suggesting very fast relaxation times of ^{207}Pb nuclei on the time scale of the NMR window, which is attributed to the slowing down of Cu^{2+} spins at low T. Such a wipe out of the NMR signal has been observed in a few cases and ususally the signal is recovered at low T, below a peak of $1/T_1$ at the transition temperature resulting from the critical slowing down of the spin dynamics [25–28]. At variance, here we did not recover the NMR signal intensity even at 50 mK implying the persistence of slow spin dynamics at very low T. This is in perfect agreement with the μSR data and confirms the dynamical nature of the ground state. The tiny broad signal detected at 0.7 K may then be related to the minority spin fraction undergoing the magnetic transition at 0.87 K. The gaussian line shape of this remaining signal suggests a disordered, spin-glass like state for these spins in line with the observed hysteresis of the magnetization – as one would expect a rectangular shaped powder average spectrum in a LRO phase [29]. From now on, we will concentrate on the NMR results in the T-range $T > 1$ K where all of the bulk spins are probed.

At high temperature, the NMR line shift ^{207}K scales with the macroscopic susceptibility χ : $^{207}K = \frac{A_{hf}}{N_A}\chi + K_0$, where A_{hf} is the hyperfine coupling constant and represents the hyperfine interaction between Cu electron spin and ^{207}Pb, N_A is the Avogadro's number, and K_0 is the T-independent chemical shift. We obtain A_{hf} = (1$\pm$ 0.05) T/μ_B and K_0= –0.05% from a linear fit of ^{207}K vs χ. The T-dependent part of the NMR line shift, K_{spin}, proportional to the spin part of the local susceptibility, is shown in Fig.4(a). The χ and K_{spin} are well reproduced by the high temperature series expansion (HTSE) and (7,7), (8,7) Padé approximants for the Heisenberg model on the hyperkagome lattice with an AFM coupling strength of $J/k_B \approx$ (14 $\pm$ 1)K between Cu spins [20, 30]. Below about 10 K, the local susceptibility tracked by ^{207}K slightly deviates from the macroscopic one, pointing to the contribution of a tiny 0.4(3)% fraction of quasi-free spin (or so called orphan spins) to the latter, and is almost constant down to 1 K [19]. The saturation at a finite and rather a high value of the local susceptibility at low T is quite similar to the case of $Na_4Ir_3O_8$ and contrasts with many 2D frustrated AFM where the local susceptibility exhibits a broad maximum at a fraction of J/k_B [5, 31]. Furthermore, given that no large deviation is observed between the macroscopic χ and ^{207}K down to 1 K one can infer from the magnetization data (shown in Fig. 1) that the intrinsic susceptibility does not vary much either below 1 K. In particular, it seems unlikely that a spin gap larger than ~ 0.45 K ($\approx \theta/50$) opens up which is confirmed by the existence of fluctuating local fields at temperatures as low as 50 mK.

Further insight into the spin correlations is provided by the ^{207}Pb spin-lattice relaxation T_1 measurements. As shown in Fig. 4(b) $1/T_1$ varies rather weakly with temperature, decreasing by a factor ~ 3 from its maximum at 300 K down to its minimum at 2 K, ruling out the possibility of a spin gap larger than 1 K in PCTO. Different T-regimes can still be distinguished. Upon cooling from high T, $1/T_1$ progressively decreases down to $\sim$ 20 K where it shows a marked kink and a steeper variation which fits to a sublinear power law $T^{0.4}$. This change below $T \sim \theta$, corresponding to the saturation of the local susceptibility, has to be related to the emergence of short range spin-correlations. This evolution can be compared to the one of the 2D spin liquid Herbertsmithite $T^{0.7}$ [5] and to the theoretical prediction of power law behaviors for critical spin liquids [32, 33]. However, contrary to these latter cases, the evolution of $1/T_1$ changes here again below about 2 K where it sharply increases. The increase of $1/T_1$ below 2 K evidences a slowing down of the spin dynamics consistent with the μSR results.

The compound $PbCuTe_2O_6$ appears as one rare example of a 3D AFM exhibiting a dynamical ground state, *i.e.* with no on-site frozen moments. This is all the more striking since first principles calculations suggest a high connectivity of the magnetic lattice ($z = 8$) resulting from three different AFM interactions of comparable strengths [16, 34]. Whether these interactions compete and eventually enhance the magnetic frustration as for instance in kapellasite [35, 36] or reduce the strong geometric frustration of the hyperkagome lattice generated by the dominant (*n.n.*) interaction requires a detailed study of the S = 1/2 Heisenberg model with all three interactions. Despite the complexity of the magnetic model, it is instructive to compare our results to the prototype material $Na_4Ir_3O_8$ for the 3D quantum hyperkagome model and related theories. Let us remind that in the case of the iridate hyperkagome, spin-orbit coupling leads to an effective $J_{\rm eff}$ = 1/2 Heisenberg model still under discussion, while such a model is the natural starting point in $PbCuTe_2O_6$. Also, the recent experimental work has shown that $Na_4Ir_3O_8$ experiences a magnetic transition below $T = 7$ K [14, 15], at variance with $PbCuTe_2O_6$ where no freezing has been detected. Now in the spin liquid phases of both compounds, the NMR shifts are found to saturate at a rather high value at low T, a feature that is best accounted for in a fermionic description of the magnetic excitations on the hyperkagome lattice leading to a spinon Fermi surface and a constant Pauli-like susceptibility [17, 18]. The absence of a large spin-gap in $PbCuTe_2O_6$ rules out the alternative possibilities of a

valence bond crystal or a topological spin liquid ground state suggested for the hyperkagome model [12, 37]. In the fermionic framework, the T^{α} ($\alpha \sim 2$ in strong applied field) behavior of the heat capacity observed below ~ 0.6 K [16] is not predicted and requires an instability - namely a partial gap opening- of the spinon Fermi surface. The strong slowing down of the spin dynamics shown by the μSR and NMR results at about 1 K could be the signature of such a crossover between two different spin liquids. Further, a partial gapping of the spinon Fermi surface at ~ 1 K resulting in a reduced density of spinon excitations may help in understanding the weak field dependence of the gaussian-like μSR relaxation, tentatively attributed to sporadic fluctuations below about 1 K.

To conclude, our investigations at low temperatures by magnetization, μSR, and NMR reveal that $PbCuTe_2O_6$ is a promising 3D antiferromagnet with S = 1/2 where strong frustration leads to a spin liquid behavior. This rare case invokes for an in depth investigation of the appropriate magnetic Hamiltonian, including for instance high temperature series expansion, together with theoretical developments in a fermionic approach. In this context our results together with those in Ref. [16] give strong constraints on the possible ground states. In view of the relatively weak coupling strength, the effect of substitutions, application of external pressure, and local probe experiments at higher magnetic fields might offer an appealing possibility to tune the magnetism of PCTO and to explore further insights into its magnetic properties.

We acknowledge R. R. P. Singh for discussions on HTSE and P. Wiecki for some T_2 measurements. PK acknowledges support from the European Commission through Marie Curie International Incoming Fellowship (PIIF-GA-2013-627322). The research was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering. Ames Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358. BK thanks DST INSPIRE faculty scheme to carry out the research work. This work was also supported by the French Agence Nationale de la Recherche under Grants "SPINLIQ" No. ANR-12-BS04- 0021, by Université Paris-Sud Grant MRM PMP and by a SESAME grant from Région Ile-de-France.

*khuntia@lps.u-psud.fr

[1] L. Balents, Nature **464**, 199 (2010) and references therein.
[2] C. Lacroix, P. Mendels, and F. Mila, *Introduction to Frustrated Magnetism*, Springer Series in Solid-State Sciences (Springer, New York), Vol. 164.
[3] S. Sachdev, Nature Physics **4**, 173 (2008).
[4] P. Mendels, F. Bert, M. A. de Vries, A. Olariu, A. Harrison, F. Duc, J. C. Trombe, J. S. Lord, A. Amato and C. Baines, Phys. Rev. Lett. **98**, 077204 (2007).
[5] A. Olariu, P. Mendels, F. Bert, F. Duc, J. Trombe, M. de Vries, and A. Harrison, Phys. Rev. Lett. **100**, 087202 (2008).
[6] T.-H. Han, J. S. Helton, S. Chu, D. G. Nocera, J. A. Rodriguez-Rivera, C. Broholm, and Y. S. Lee, Nature **492**, 406 (2012).
[7] Y. Shimizu, K. Miyagawa, K. Kanoda, M. Maesato, and G. Saito, Phys. Rev. Lett. **91**, 107001 (2003).
[8] T. Itou, A. Oyamada, S. Maegawa, and R. Kato, Nature Physics **6**, 673 (2010).
[9] T. Aharen, J. E. Greedan, C. A. Bridges, A. A. Aczel, J. Rodriguez, G. MacDougall, G. M. Luke, T. Imai, V. K. Michaelis, S. Kroeker, H. Zhou, C. R. Wiebe, and L. M. D. Cranswick, Phys. Rev. B **81**, 224409 (2010).
[10] M. A. de Vries, J. O. Piatek, M Misek, J. S. Lord, H. M. Rønnow, and J.-W. G. Bos, New J. Phys. **15**, 043024 (2013).
[11] M. J. P. Gingras, and P. A. McClarty, Rep. Prog. Phys. **77**, 056501(2014).
[12] M. J. Lawler, H.-Y. Kee, Y. B. Kim, and A. Vishwanath, Phys. Rev. Lett. **100**, 227201 (2008).
[13] Y. Okamoto, M. Nohara, H. A.-Katori, H. Takagi, Phys. Rev. Lett. **99**, 137207 (2007).
[14] R. Dally, T. Hogan, A. Amato, H. Luetkens, C. Baines, J. Rodriguez-Rivera, M. J. Graf, and S. D. Wilson, Phys. Rev. Lett. **113**, 247601 (2014).
[15] A. C. Shockley, F. Bert, J-C. Orain, Y. Okamoto, and P. Mendels, Phys. Rev. Lett. **115**, 047201(2015).
[16] B. Koteswararao *et al*., Phys. Rev. B **90**, 035141(2014).
[17] M. J. Lawler, A. Paramekanti, Y. B. Kim, and L. Balents, Phys. Rev. Lett. **101**, 197202 (2008).
[18] Y. Zhou, P. A. Lee, T.-K. Ng, and F.-C. Zhang, Phys. Rev. Lett. **101**, 197201 (2008).
[19] It is noticeable that even at very low T, M/H is little field dependent suggesting sizeable AFM interactions among all spins in the sample and a small amount of quasi-free or "orphan spins" commonly observed in frustrated materials.
[20] Supplemental Material: It comprises of experimental details pertaining to magnetization, NMR, and μSR.
[21] T. Moriya, Prog. Theor. Phys. **16**, 23 (1956).
[22] R. Hayano *et al*., Phys. Rev. B **20**, 850 (1979).
[23] Y. J. Uemura, A. Keren, K. Kojima, L. P. Le, G. M. Luke, W. D. Wu, Y. Ajiro, T. Asano, Y. Kuriyama, M. Mekata, H. Kikuchi, and K. Kakurai, Phys. Rev. Lett. **73**, 3306 (1994).
[24] D. Bono, P. Mendels, G. Collin, N. Blanchard, F. Bert, A. Amato, C. Baines, and A. D. Hillier, Phys. Rev. Lett. **93**, 187201 (1994).
[25] A. W. Hunt, P. M. Singer, K. R. Thurber, and T. Imai, Phys. Rev.Lett. **82**, 4300 (1999).
[26] D. A. Levitt and R. E. Walsted, Phys. Rev. Lett. **38**, 178 (1977).
[27] L. Limot, P. Mendels, G. Collin, C. Mondelli, B. Ouladdiaf, H. Mutka, N. Blanchard, and M. Mekata, Phys. Rev. B **65**, 144447 (2002).
[28] A. Olariu, P. Mendels, F. Bert, B. G. Ueland, P. Schiffer, R. F. Berger, and R. J. Cava, Phys. Rev. Lett. **97**, 167203 (2006).
[29] Y. Yamada and A. Sakata, J. Phys. Soc. Jpn. **55**, 1751 (1986).
[30] J. Oitmaa, C. Hamer, and W. Zheng, *Series Expansion Methods for Strongly Interacting Lattice Models* (Cambridge University Press, Cambridge, 2006). R. R. P Singh and J. Oitmaa, Phys. Rev. B **85**, 104406 (2012).
[31] J. A. Quilliam, F. Bert, R. H. Colman, D. Boldrin, A. S.

Wills, and P. Mendels, Phys. Rev. B **84**, 180401(R) (2011).
[32] M. Hermele, Y. Ran, P.A. Lee and X.-G. Wen Phys. Rev. B **77** 224413 (2008).
[33] Y. Huh, L. Fritz and S. Sachdev, Phys. Rev. B **81**, 144432 (2010).
[34] Taking into account the calculated value for the three interactions, one can compute an effective $z_{\rm eff}$ = 6.6 such that $z_{\rm eff}J$ = 4J +2 (0.8J) + 2(0.5J).
[35] B. Fåk, E. Kermarrec, L. Messio, B. Bernu, C. Lhuillier, F. Bert, P. Mendels, B. Koteswararao, F. Bouquet, J. Ollivier, A. D. Hillier, A. Amato, R. H. Colman, and A. S. Wills, Phys. Rev. Lett. **109**, 037208 (2012).
[36] E. Kermarrec, A. Zorko, F. Bert, R.H. Colman, B. Koteswararao, F. Bouquet, P. Bonville, A.D. Hillier, A. Amato, J. van Tol, A. Ozarowski, A.S. Wills and P. Mendels, Phys. Rev. B **90** 205103 (2014).
[37] E. J. Bergholtz, A. M. Laeuchli, and R. Moessner, Phys. Rev. Lett. **105**, 237202 (2010).

Figure Captions

Fig 1(Color online) (a) Temperature dependence of the magnetic susceptibility in several applied fields. The bottom left inset shows a partial view of the crystal structure of $PbCuTe_2O_6$. The top right inset shows the T-dependence of magnetic specific heat by T (C_m/T) in 0 T [adapted from Ref.[16]).

Fig. 2 (Color online) (a) Field dependence of muon polarization $P_z(t)$ at $T = 0.1$ K. The solid line correspond to dynamical Kubo-Toyabe model (DKT) as explained in the text. (b) T-dependence of the relaxation rate obtained from the stretched exponential fit. The inset shows the T-dependence of the stretched exponent.

Fig. 3 (Color online) (a) Temperature evolution of field swept ^{207}Pb NMR spectra at 63.5 MHz (b) The temperature dependence of NMR signal intensity and the inset shows the T dependence of $1/T_2$ at 63.5 MHz.

Fig. 4 (Color online) (a) Temperature dependence of the^{207}Pb shift and the magnetic spin susceptibility χ_{spin}. The solid lines correspond to HTSE up to order 15 and 16 for the hyperkagome lattice and extrapolations using Padé approximation (adapted from [30]). (b) T- dependence of the spin-lattice relaxation rate at three frequencies. The solid line is a fit to T^α giving $\alpha = 0.4 \pm 0.05$.

SUPPLEMENTAL

Spin Liquid State in the 3D Frustrated Antiferromagnet $PbCuTe_2O_6$: NMR and μSR Studies

Magnetic Susceptibility

Magnetization measurements in different applied magnetic fields were performed using a Quantum Design (QD) MPMS at high temperature. The temperature dependence of magnetic susceptibility in the temperature range 0.45 K to 10 K measured in a commercial MPMS-7T SQUID magnetometer equiped with a ^{3}He low temperature insert in various applied magnetic fields up to 7 T.

Muon Spin Relaxation (μSR)

We have performed μSR measurements in zero field and in applied magnetic fields at the Paul Scherrer Institute facility in a helium flow cryostat on the GPS spectrometer and in the dilution fridge of the LTF spectrometer.

Shown in Fig. S1 is the zero field muon μ^+ polarizations at different temperatures down to 20 mK and the solid lines are fits to the stretched exponential $P_z(t) = P_0 \exp[-(\lambda t)^\beta]$ of the muon polarization. The relaxation rate, λ, thus obtained increases with decreasing temperature suggesting the slowing down of spin fluctuations which is shown in Fig. 2 of the main text of the manuscript. The constant value of λ beolw 0.5 K suggests the presence of a short-range spin correlations and dynamical ground state inherent to the slow magnetic fluctuation of Cu^{2+} spins. The temperature dependence of stretched exponent (β) is shown as an inset in Fig. 2(b) of the main text.

Nuclear Magnetic Resonance (NMR)

^{207}Pb (I = 1/2; $\frac{\gamma_n}{2\pi}$=8.874 MHz/T) NMR measurements were carried out using a home made phase-coherent spin-echo pulse spectrometer in an extended temperature range with a ^{3}He-^{4}He dilution refrigerator (Kelvinox MX100, Oxford instruments) and using a He flow cryostat installed at Ames Laboratory. The ^{207}Pb-NMR spectra were obtained by sweeping the magnetic field. As a further measure to understand the low temperature magnetism, we have performed nuclear spin-spin relaxation time (T_2) measurements (shown in the inset of Fig. 3(b) of the main text). The T_2 value at each temperature was obtained by fitting the transverse magnetization, M_{xy} (t) = $M_0 e^{-2t/T_2}$, where M_0 is the initial magnetization and t is the delay between two *rf* pulses ($\pi/2 - t - \pi$). The raw NMR signal intensity at each temperature was determined by extrapolating M_{xy} to t = 0 in the recovery of the transverse magnetization. The signal intensity thus obtained was multiplied by temperature to compensate for the Boltzmann factor. The temperature dependence of normalized signal intensity in $PbCuTe_2O_6$ at 63.5 MHz thus obtained is shown in Fig. 3(b) of main text of the manuscript. It is found that $1/T_2$ increases continuously on lowering the temperature, which is contrary to conventional long range ordered antiferromagnet wherein one expects a peak in $1/T_2$.

Shown in the left panel of Fig. S2 is the temperature dependence of the NMR spin susceptibility compared with that of the bulk magnetic susceptibility in the whole tempearure range of the present investigation. The little in-

crease of K_{spin} below 1 K is the shift of the residual signal ascribed to a tiny fraction of defect spins present in the polycrystalline sample.

The spin lattice relaxation time (T_1) at each temperature was determined by fitting the recovery of the nuclear magnetization $M_z(t) = M(\infty)(1–e^{-t/T_1})$ towards its equilibrium value $M(\infty)$ after a single saturation pulse (here $M_z(t)$ and $M(\infty)$ are the nuclear magnetization at time t after the saturation and equilibrium nuclear magnetization at $t \rightarrow \infty$ respectively). The recovery of longitudinal magnetization $M_z(t)$ could consistently be fitted with a single exponential function in the temperature and magnetic field ranges of the present investigation, which indicates the presence of single Pb site in the host lattice without structural distortion. The NMR shift (K) probes intrinsic spin susceptibility $\chi(q = 0, \omega = 0)$ of the system under study.The spin-lattice relaxation rate tracks the low energy spin fluctuations and is expressed as the mean of the imaginary part of dynamic spin susceptibility $\chi''(q,\omega)$ in the q-space *i.e.*, $1/T_1T \propto \sum \mid A_{hf}(q) \mid^2 \chi''(q,\omega)$, where $A_{hf}(q)$ is the form factor of the hyperfine interactions. The right panel of Fig. S2 represents the temperature evolution of $1/T_1$ in the whole temperature rage of the present investigation. As discussed in the main text, the peak in $1/T_1$ at 1 K should not be taken as evidence of a magnetic transition because it is concomitant with a huge loss of the signal intensity. The decrease of $1/T_1$ below 1 K is rather associated with the increasing of relative NMR signal from the tiny fraction of defect spins which feature a longer T_1.

Spin Susceptibility (Hyperkagome model)

The exchange interaction between the nearest neighbor Cu^{2+} spins can be expressed with Heisenberg Hamiltonian with J as exchange coupling.

$H = J \sum_{<i,j>} S_i.S_j$

The strength of the exchange interaction (J) between the nearest neighbor Cu^{2+} spins on the hyperkagome lattice, was obtained from the fitting of the magnetic susceptibility data following the high temperature series expansion (HTSE) for S = 1/2 system valid for hyperkagome lattice[1]

$\chi(T) = \frac{N_A g^2 \mu_B^2}{4k_B} \sum_0^{16} b_n (-\frac{J}{4k_B T})^n$

with series expansion coefficients b_n and the values of which can be found in Ref.[1]. The magnetic susceptibility and the intrinsic local spin susceptibilty are well explained by the nearest-neighbor Heisenberg model on a hyperkagome lattice. The HTSE extrapolations for magnetic susceptibility using (7,7) and (8,7) Padé approximants converge down to $J/4$ [1]. The fit of the magnetic susceptibility data to hyperkagome model yields an AFM coupling J/k_B = (14 $\pm$ 1) K between Cu^{2+} spins.

[1] J. Oitmaa, C. Hamer, and W. Zheng, *Series Expansion Methods for Strongly Interacting Lattice Models* (Cambridge University Press, Cambridge, 2006). R. R. P Singh and J. Oitmaa, Phys. Rev. B **85**, 104406 (2012).

Figure Captions

SM Fig. 1 (Color online) The zero field muon spin polarizations at various temperatures and the solid lines are fits to stretched exponential.

SM Fig 2. (Color online) Temperature dependence of the NMR spin susceptibility (K) and the magnetic susceptibility (χ) in the whole temperature range of the present investigation. (b) T-dependence of the spin lattice relaxation rate in the whole temperature range of the present work and the solid line is the $T^{0.4}$ behavior.

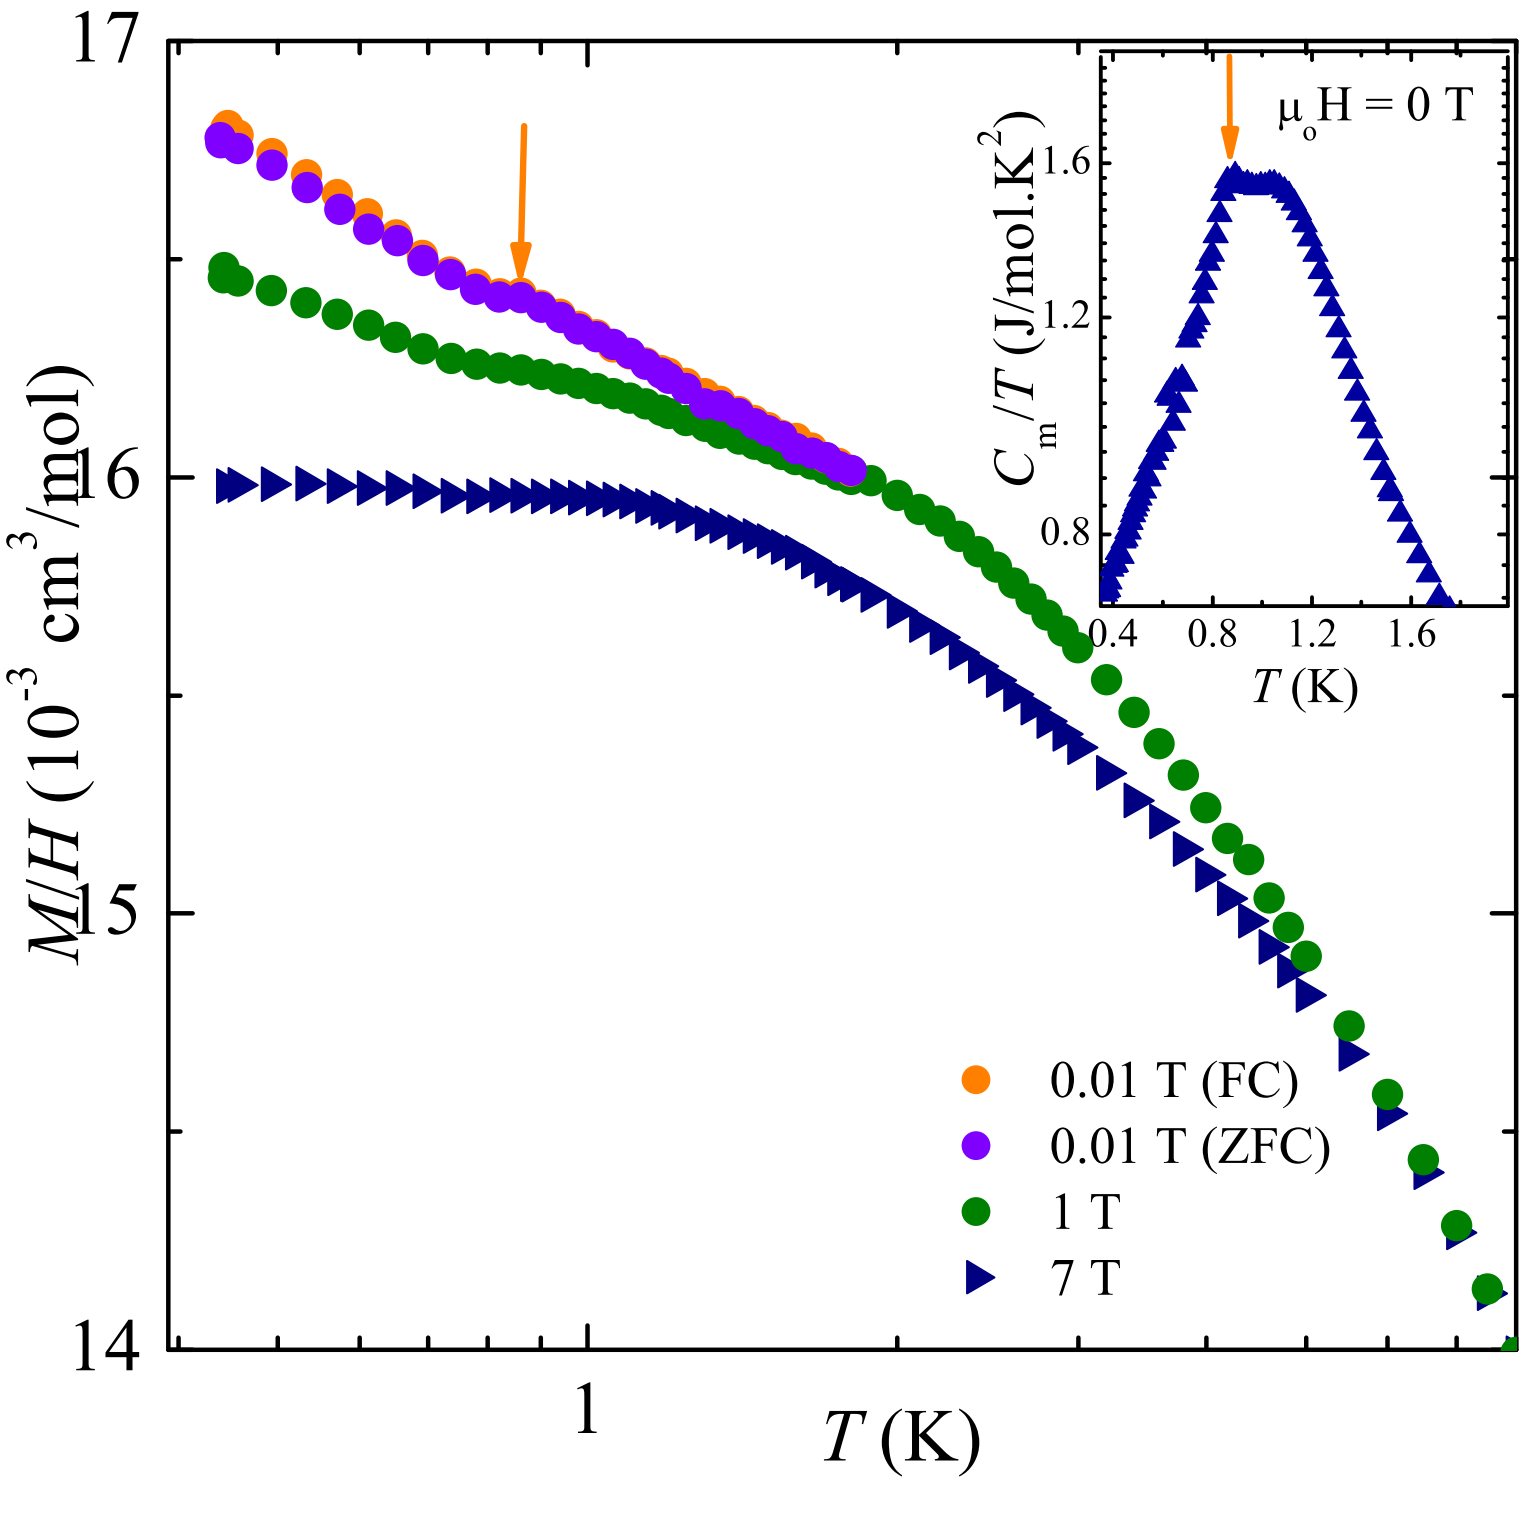
17
16
15
14
1
T (K)
M/H (10^-3 cm^3/mol)
0.01 T (FC)
0.01 T (ZFC)
1 T
7 T
μ_o H = 0 T
C_m/T (J/mol.K^2)
1.6
1.2
0.8
0.4
0.8
1.2
1.6
T (K)

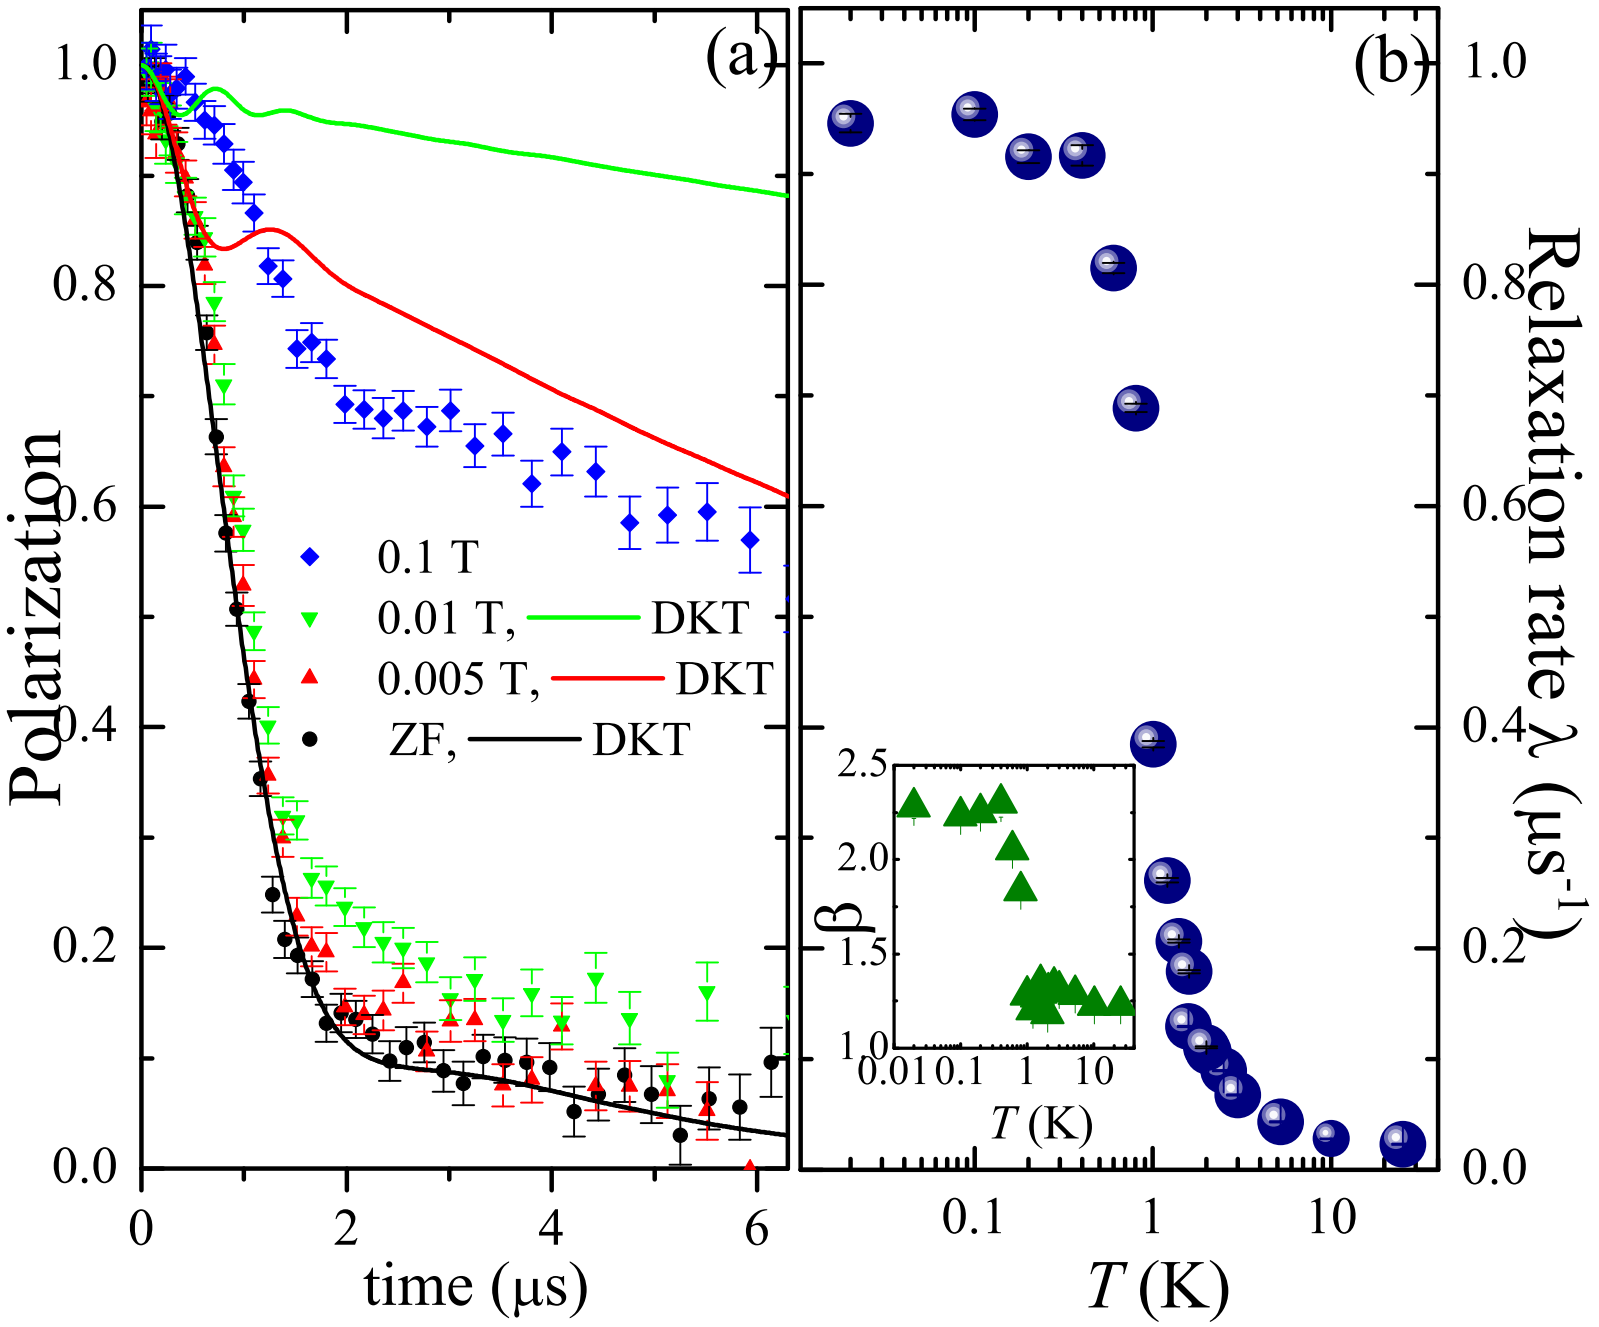
(a)
(b)
Polarization
time (μs)
0.1 T
0.01 T,
DKT
0.005 T,
DKT
ZF,
DKT
Relaxation rate λ (μs-1)
T (K)
β
T (K)

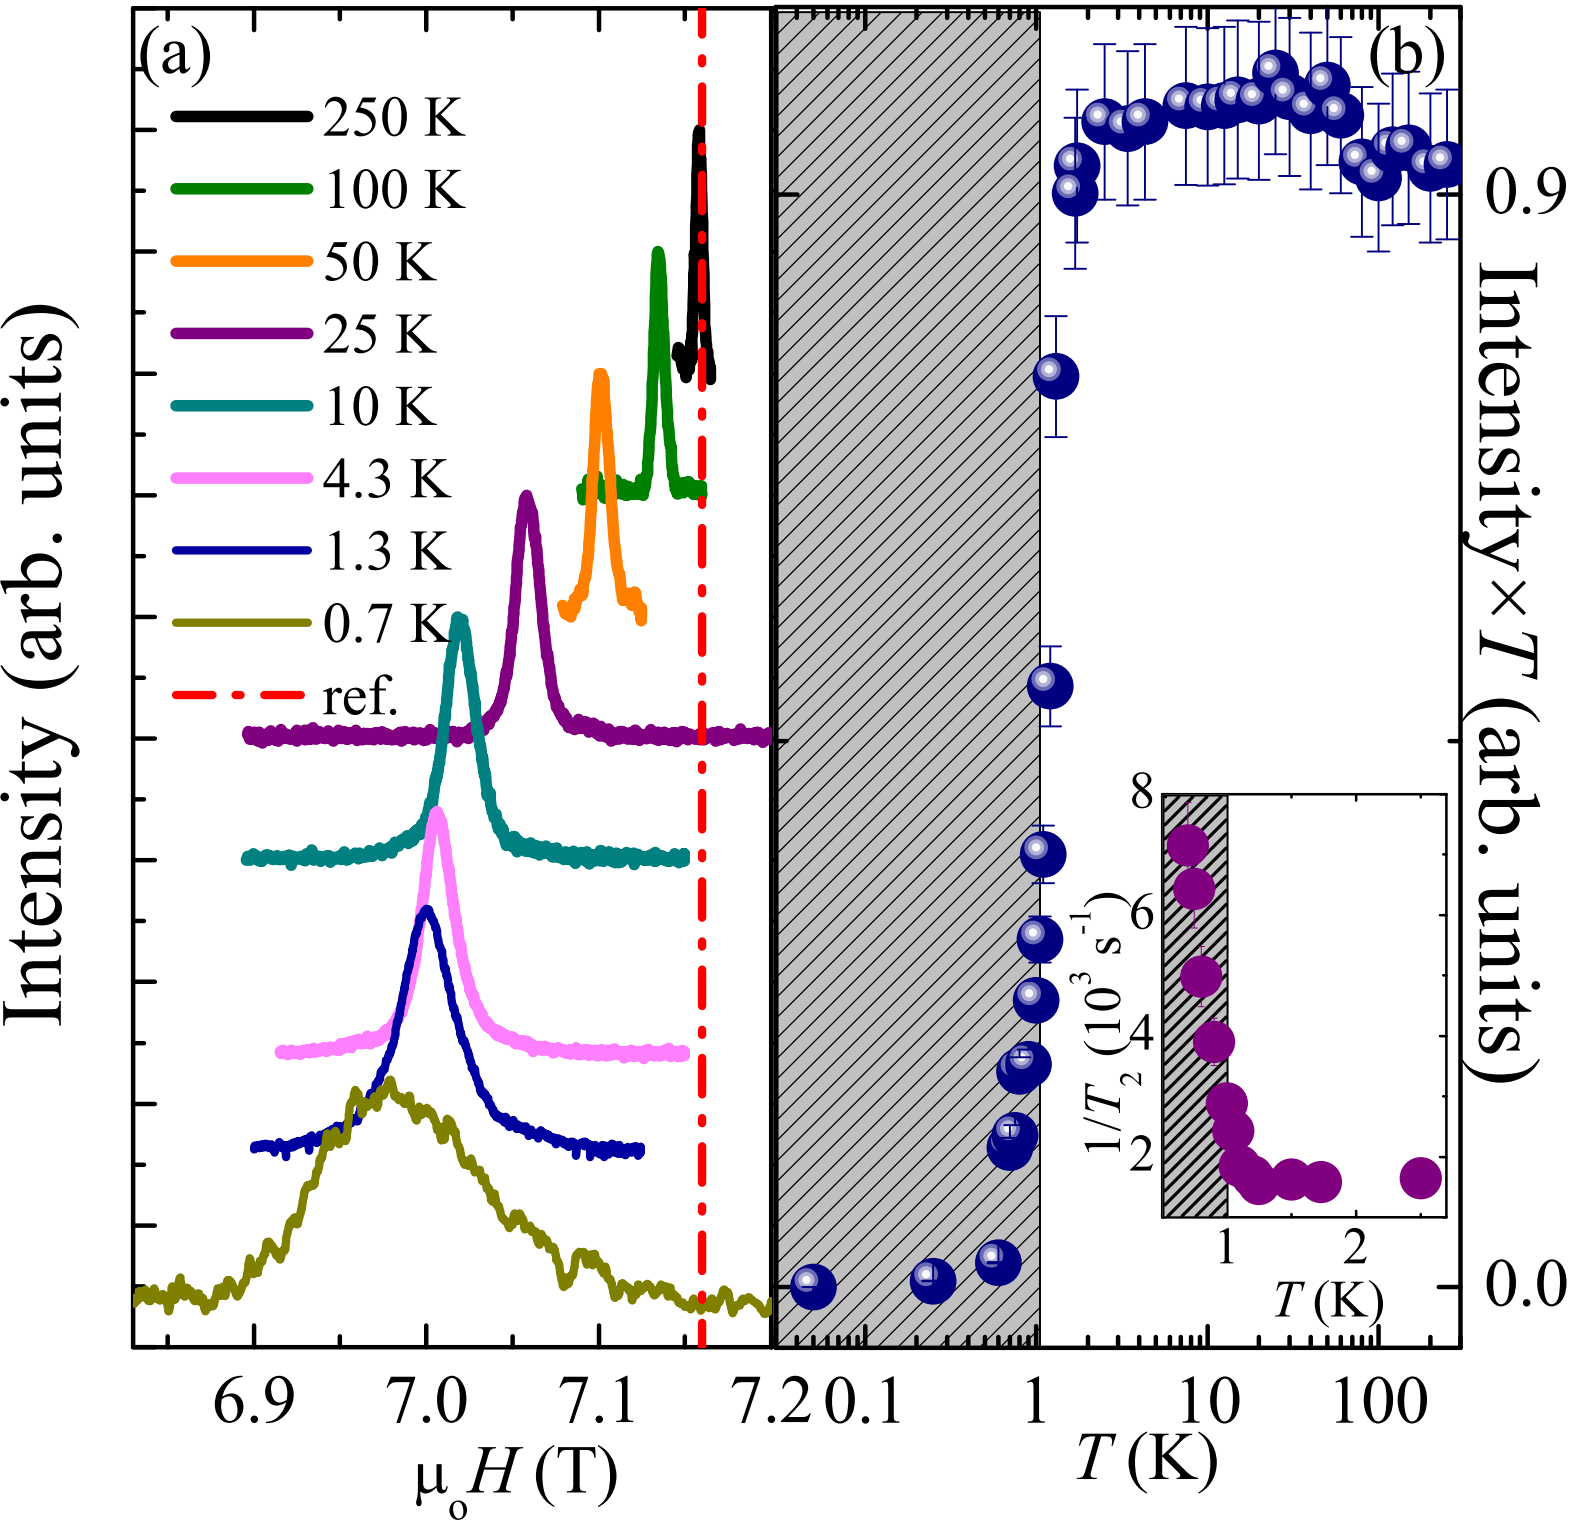
(a)
250 K
100 K
50 K
25 K
10 K
4.3 K
1.3 K
0.7 K
ref.
Intensity (arb. units)
6.9
7.0
7.1
7.2
μ0H (T)
(b)
0.9
0.0
Intensity×T (arb. units)
0.1
1
10
100
T (K)
8
6
4
2
1/T2 (10^3 s^-1)
1
2
T (K)

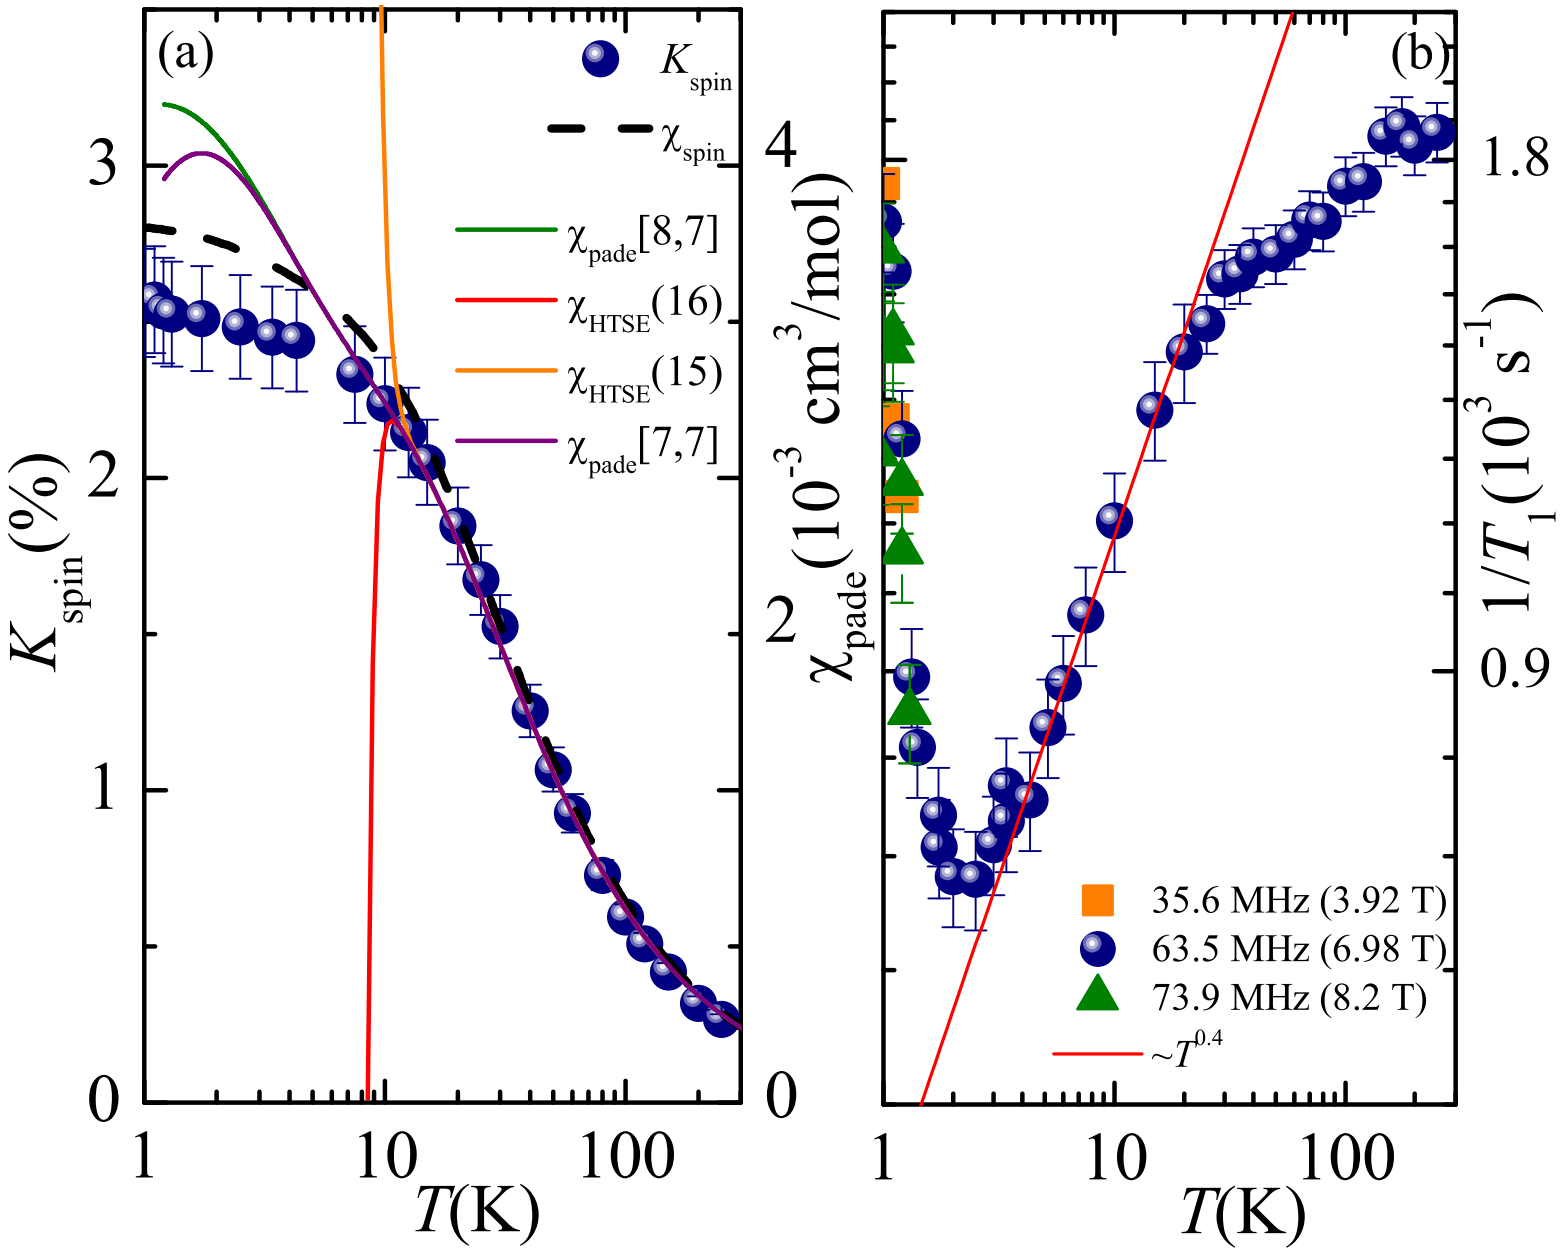
(a)
K_{spin}
χ_{spin}
χ_{pade}[8,7]
χ_{HTSE}(16)
χ_{HTSE}(15)
χ_{pade}[7,7]
K_{spin}(%)
T(K)
(b)
χ_{pade}(10^{-3} cm^3/mol)
$1/T_1$(10^3 s^{-1})
35.6 MHz (3.92 T)
63.5 MHz (6.98 T)
73.9 MHz (8.2 T)
~$T^{0.4}$
T(K)

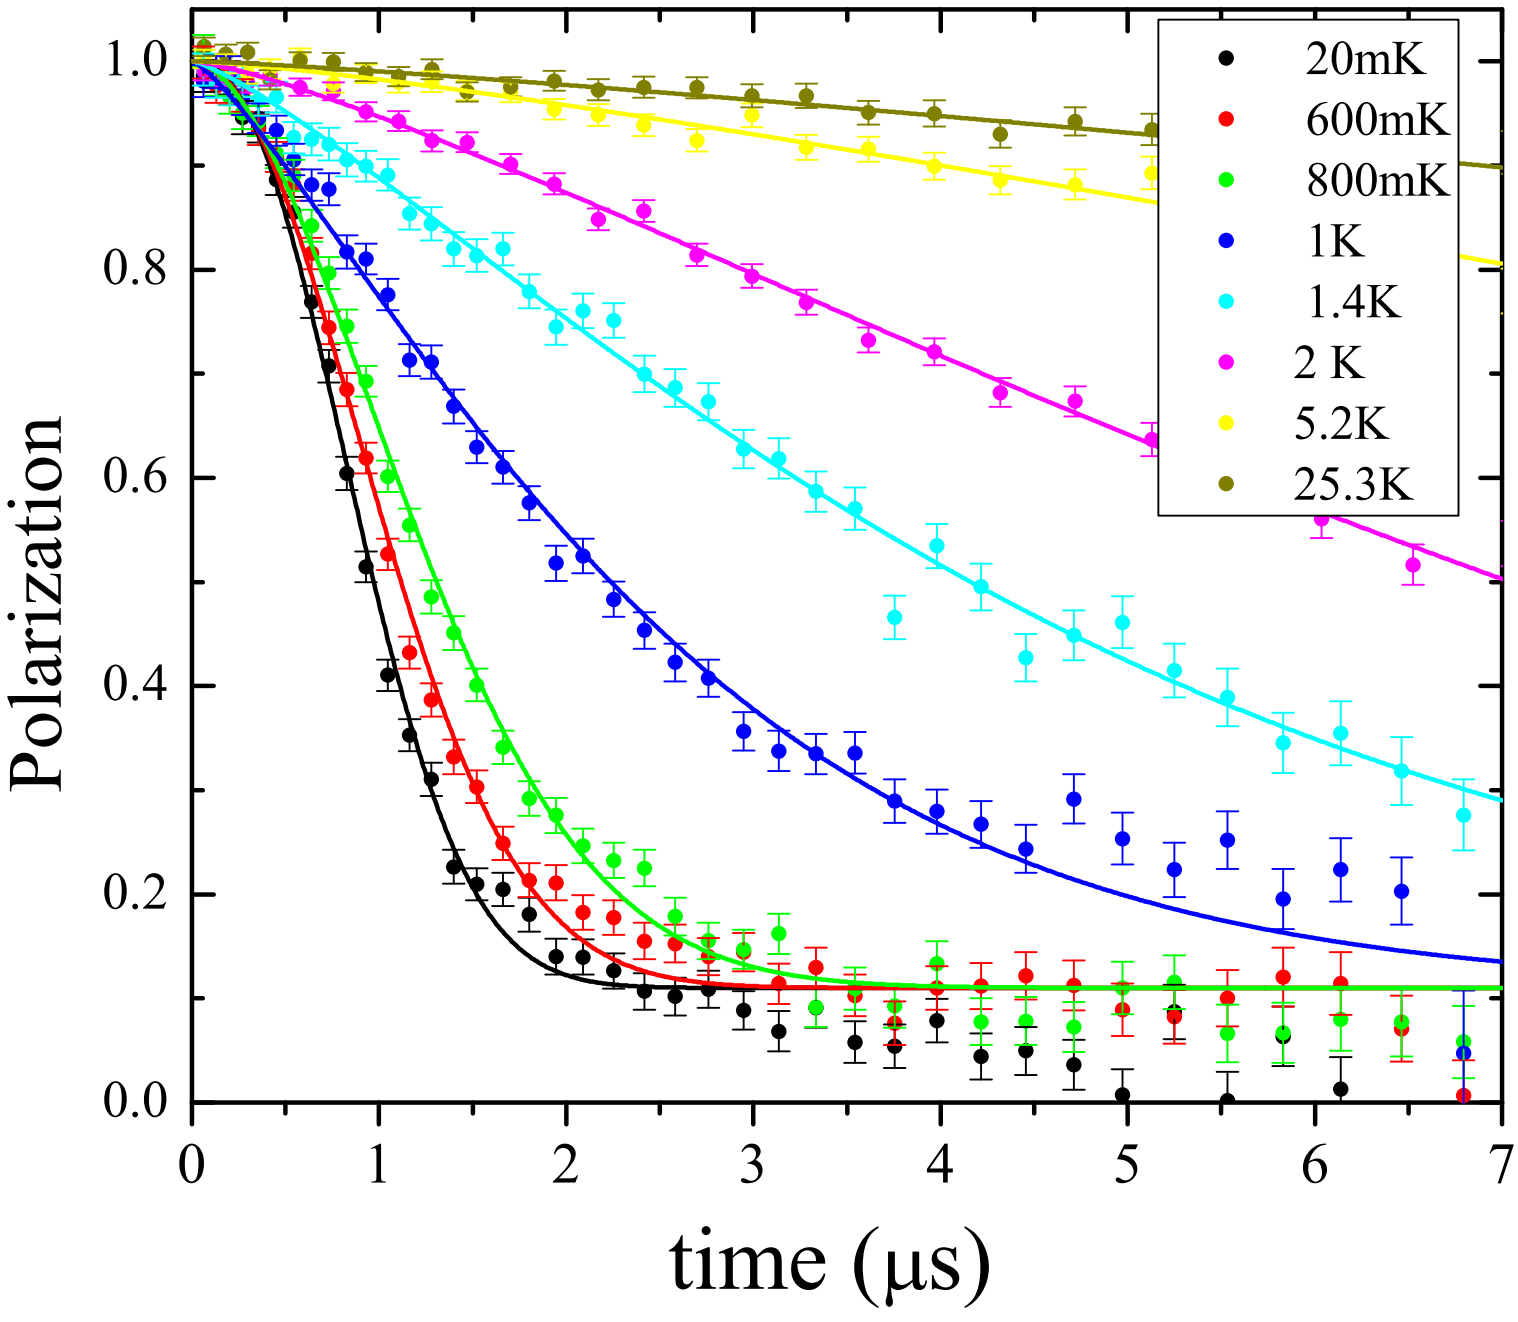
Polarization
time (μs)
1.0
0.8
0.6
0.4
0.2
0.0
0
1
2
3
4
5
6
7
20mK
600mK
800mK
1K
1.4K
2 K
5.2K
25.3K

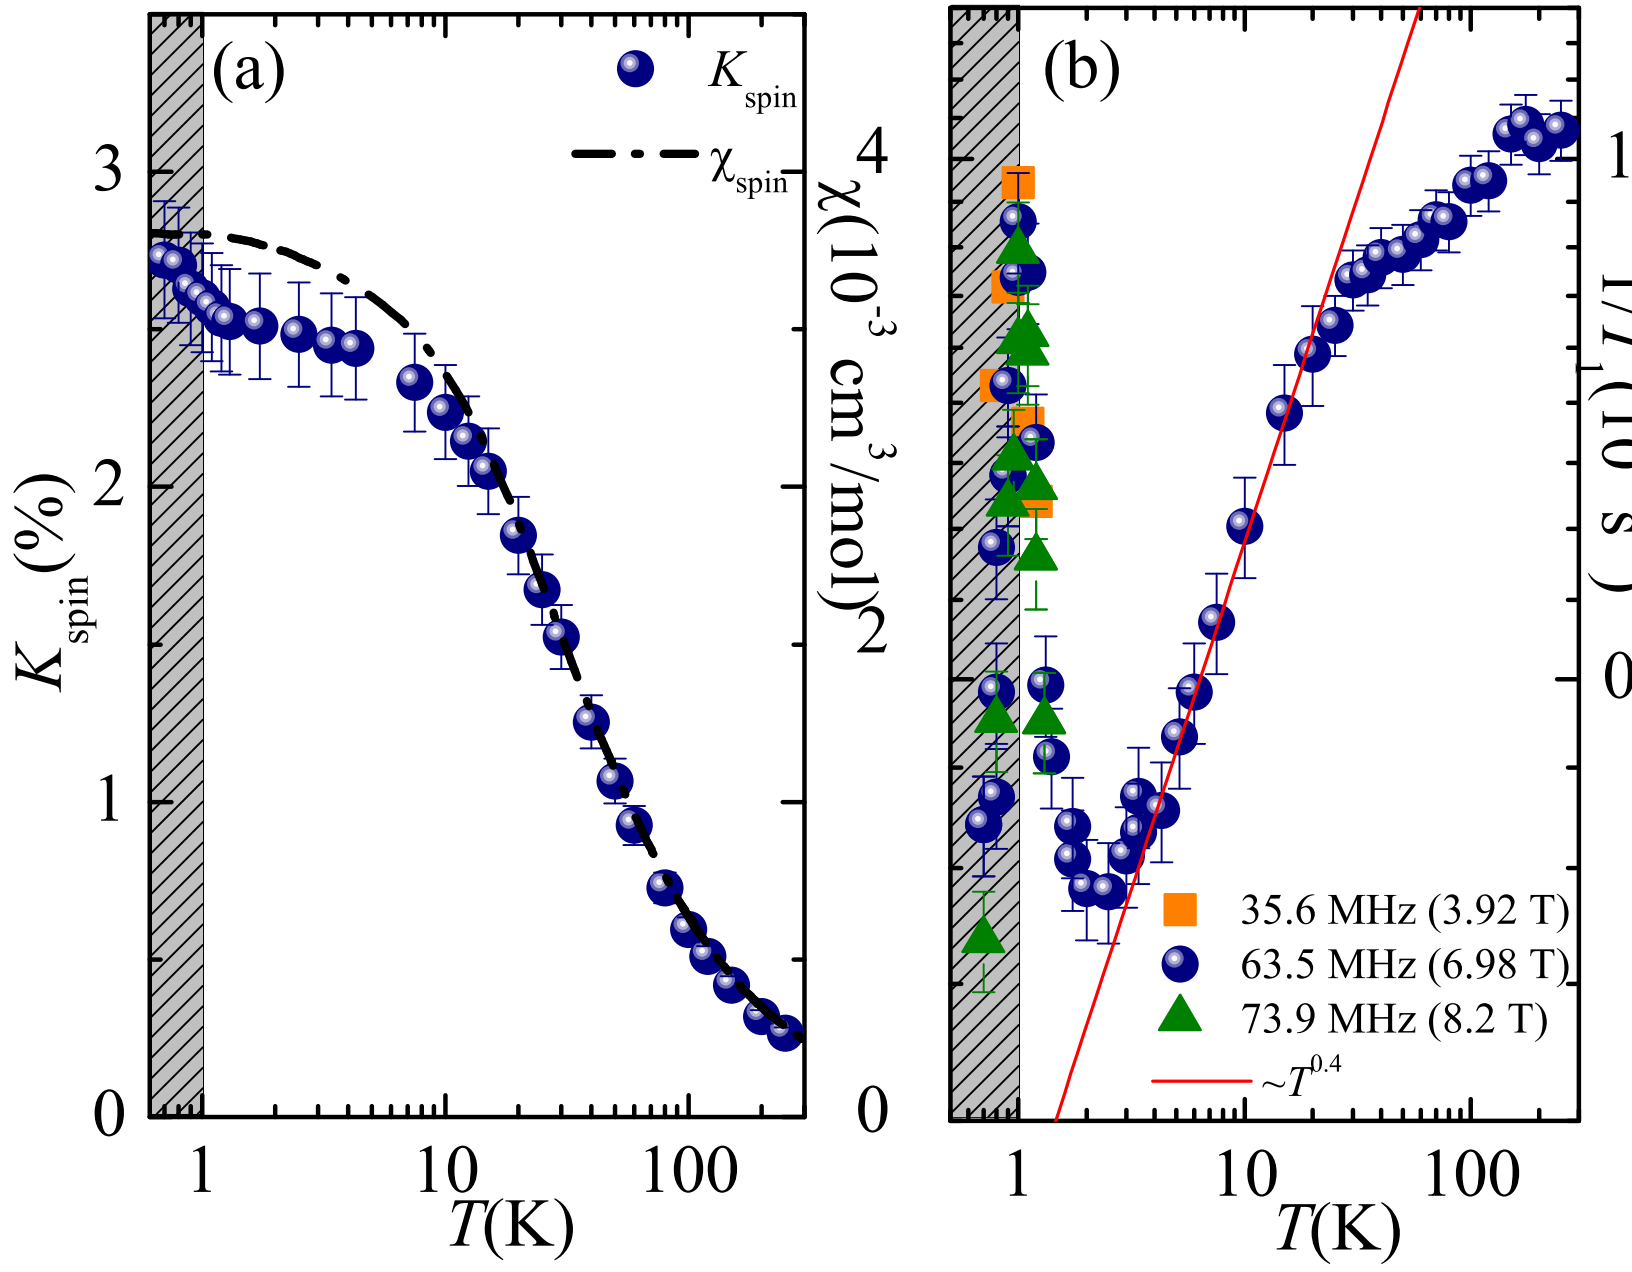
(a)
K_{spin}
χ_{spin}
K_{spin}(%)
χ(10^{-3} cm^3/mol)
T(K)
(b)
35.6 MHz (3.92 T)
63.5 MHz (6.98 T)
73.9 MHz (8.2 T)
$\sim T^{0.4}$
T(K)